

# implants

international magazine of oral implantology

2<sup>2014</sup>



## | Research

Use of allogeneic cortical granulate for external surgical sinus floor elevation

## | Case report

Surgical procedures with minimally-invasive autologous bone block graft

## | Industry report

Sinus augmentation with atelo-collagenated bovine bone graft Hypro-Oss

**ASTRA TECH  
IMPLANT SYSTEM**



# Join the **EV**olution



The new  
**ASTRA TECH Implant System™ EV**  
– now available

Learn more



[www.jointheev.com](http://www.jointheev.com)



The foundation of this evolutionary step remains the unique **ASTRA TECH Implant System BioManagement Complex**, well-documented for its long-term marginal bone maintenance and esthetic results. [www.dentsplyimplants.com](http://www.dentsplyimplants.com)

**DENTSPLY**  
IMPLANTS



Dr Roland Hille

# Dear colleagues,

**If you are one of those who want to** include field-tested and innovative implantological treatment concepts to your office and, furthermore, you wish to learn about the decisive criteria for practical techniques and materials, I am sure we will see each other at the 44<sup>th</sup> International Annual DGZI Congress on 26 and 27 September 2014 in Düsseldorf, Germany. We chose this special congress venue as Düsseldorf forms the international centre of an innovative region with a high entertainment factor.

Advanced education will usually demand some of your spare time, but with our DGZI training courses, you will have much fun and easily-applicable knowledge in exchange, ensuring both the success of your dental office and content patients.



Only you can influence this business factor, and it's the best marketing tool to gain new patients. DGZI offers you opportunities which include e-learning curriculums and master study courses that you shouldn't miss! As in the previous years, our discussion panel DGZI Kontrovers will be used for an active exchange among the speakers and their audience. This year's motto is "Stone-Age Implantology vs. Computer Games" encourages to discuss technology by posing questions such as "Which products are necessary?", "Which products are mandatory?" and "What are my general options?". In addition, we will also discuss high-level implantology which makes do without high-end technology, as each patient deserves an individual treatment concept.

Again we have assembled more than 30 speakers from Germany and around the world who will provide you with new ideas and innovative concepts.

Don't miss out on this year's International Annual DGZI Congress! Its personal atmosphere, combined with an extensive dental exhibition, will guarantee that you can "learn from the best" and enjoy immediate success. I am looking forward to seeing you in Düsseldorf!

Warm regards,

Prof. (CAI) Dr Roland Hille  
DGZI Vice President and Scientific Director

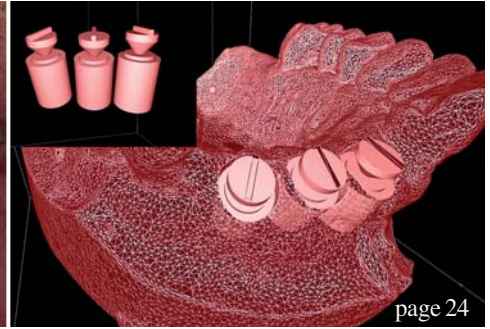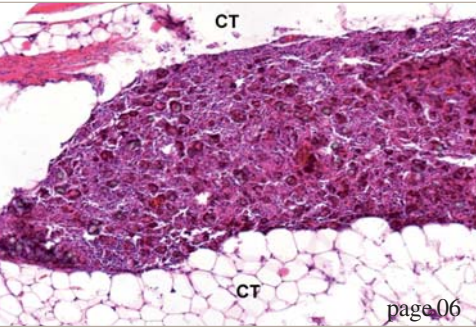

**| editorial**

03 **Dear colleagues**  
| Dr Roland Hille

**| research**

06 **Injectable bone substitute** based on  $\beta$ -TCP granules  
| Dr Dr Shahram Ghanaati *et al.*

14 **Use of allogeneic cortical granulate** for external surgical sinus floor elevation  
| Dr Phillip Wallowy & Dr Karam Kass-Elias

**| case report**

20 **Complete prosthetic restoration** in a patient with cleft palate  
| Dr Michael Peetz & Dr Thomas Hitz

**| overview**

24 **Optimized implant planning: DICOM-STL matching**  
| Dr Frank Schaefer *et al.*

**| case report**

32 **Surgical procedures with minimally-invasive autologous bone block graft**  
| Prof. Dr Sergio Alexandre Gehrke

**| industry report**

36 **Sinus augmentation** with atelo-collagenated bovine bone graft Hypro-Oss™  
| Dr Amir Gazmawe

**| interview**

40 **“The trend** towards the medium-price range has **accelerated”**  
| DT Asia Pacific

**| meetings**

44 **Biggest** international implant dentistry meeting to date  
46 **More than 120 implantologists** met for the International Bicon Symposium  
47 **Minimally invasive treatment concepts** in Lucerne  
| Jürgen Isbaner, Chief editor DT D-A-CH

**| news**

42 **Manufacturer News**  
48 **News**


**| about the publisher**

50 | imprint



Cover image courtesy of  
CAMLOG Biotechnologies AG  
[www.camlog.com](http://www.camlog.com)

Original Background: ©SkillUp  
Artwork by Josephine Ritter, OEMUS MEDIA AG.

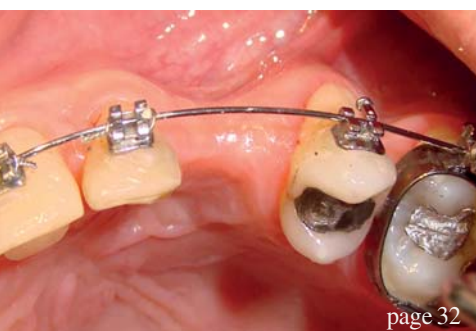



5<sup>TH</sup> INTERNATIONAL

# CAMLOG CONGRESS

26<sup>TH</sup> – 28<sup>TH</sup> JUNE 2014

VALENCIA, SPAIN



# CONGRESS OF THE YEAR

REGISTER  
NOW

No claims without proof! And proof we have! Not only do the delegates give us enthusiastic feedback, they keep registering again and again. Not surprising, having attended once, you never want to miss another congress! Focused competence, practical benefits and the lively atmosphere at the congress speak for themselves. Register for the congress - we look forward to welcoming you!

**THE EVER EVOLVING WORLD OF IMPLANT DENTISTRY**

camlogfoundation

More information and registration:  
[www.camlogcongress.com](http://www.camlogcongress.com)



# Injectable bone substitute based on $\beta$ -TCP granules

## Results from an *in-vivo* analysis in Wistar rats

Authors\_M. Barbeck, J. Lorenz, C. Landes, R.A. Sader, C.J. Kirkpatrick & S. Ghanaati, Germany

### \_Introduction

In the recent years biomaterial research has focused on developing a reliable and safe alternative to autologous bone for augmentation in case of a reduced local bone amount. As autologous bone has osteoinductive, osteoconductive and osteogenic properties, it is postulated to be the gold standard in peri-implant hard tissue augmentation.<sup>1</sup> Xenogenic bone substitutes, originating from animals of different species and processed in different steps, are well researched and accepted from both surgeons and patients.<sup>2</sup> Alloplastic bone substitutes from synthetically manufactured hydroxyapatite (HA), beta-tricalcium phosphate ( $\beta$ -TCP) or a mixture of these two compounds have been reported to be biocompatible, degradable and osteoconductive.<sup>3-7</sup>


During integration in the host tissue, parameters such as the potential induction of an inflammatory response, the biomaterial vascularisation and degradation play an important role.<sup>8-14</sup> By modifying the chemical and physical characteristics of a biomaterial, i.e. its chemical composition and its surface structure morphology and porosity, it seems to be possible to tailor alloplastic bone substitute materials individually to specific requirements.<sup>9</sup> From a number of *in vitro* and *in vivo* trials it is known that beside the chemical composition, the granule size also has a significant impact in the degradation behaviour of synthetic bone substitute materials. Granules with a mean size larger than 500  $\mu\text{m}$  and a low porosity are more slowly degraded and resist the ingrowth of connective tissue in the implantation bed more than granules smaller than 50  $\mu\text{m}$ .<sup>9,12,15-17</sup> However, small granules might be more suitable for different kinds of defect classes.

With a combination of small, pure-phase  $\beta$ -TCP granules, which serve as bioactive fillers, and a carrier matrix of methylcellulose (MC) and hyaluronic acid (HY), the fast degradation of the small granules and the connective tissue influx might be prevented by the aqueous phase. All three components, the  $\beta$ -TCP, the MC and the HY are known to be biocompatible<sup>2-6,18-25</sup> and have optimal mechanical and regulating properties, which are favourable for tissue engineering and regeneration.<sup>20-35</sup> Additionally, biomaterial might also be easier to handle, as it is paste-like and therefore injectable into the augmentation site.

The aim of the present study was to investigate the inflammatory response, as well as the overall integrity within the implantation bed, the degradation behav-

**Fig. 1** The tissue reaction to the triphasic bone substitute material at day 3 after implantation:

- a) a total scan of the bone substitute, which was located within the connective tissue (CT: connective tissue; EP: Epidermis; OR: outer cell-rich region; IR: inner region) (H&E-staining, total scan, 100x magnification);
- b) the infiltration of mononuclear cells into the outer region (Movat's pentachrome staining, 400x magnification; scale bar = 100  $\mu\text{m}$ );
- c) inner region (IR), in which the  $\beta$ -TCP granules (TCP) were embedded (asterisks) (Movat's pentachrome staining, 100x magnification; scale bar = 100  $\mu\text{m}$ ).

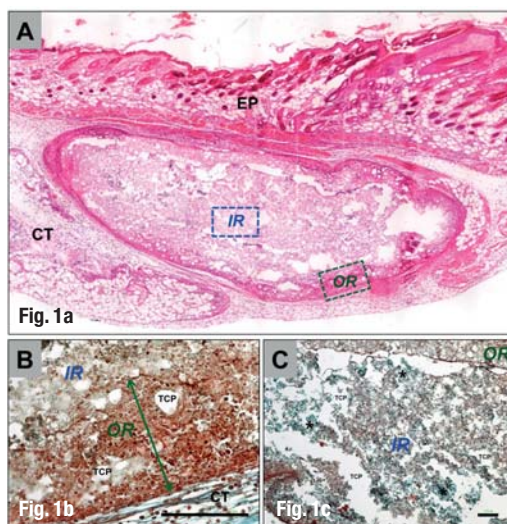



# More than an implant. A sense of trust.

The Straumann® Dental Implant System is a worldwide leading solution for general practitioners and specialists. Our commitment to research ensures high quality backed by independent science. Producing innovations that improve patient care has made us a trusted business partner in over 70 countries.


[www.straumann.com](http://www.straumann.com)

**60** YEARS

  
simply doing more

**Fig. 2\_** The tissue reaction to the triphasic bone-substitute material at day 10 after implantation:

- a) an overview of the total implant area by means of a total scan. (H&E-staining, total scan, 100x magnification);
- b) the outer region (OR, double head arrow), which was distinguishable from the inner region (IR). (red arrows: vessels; arrow heads: giant cells; H&E-staining, 200x magnification; scale bar = 100  $\mu$ m);
- c) ingrowth of connective tissue into the outer region of the implanted paste-like bone-substitute material. (red arrows: vessels; red asterisks: polymer solution; Movat's pentachrome staining, 400x magnification; scale bar = 100  $\mu$ m);
- d) multinucleated giant cells within the outer region; red arrow heads: TRAP positive multinucleated giant cells; black arrow heads: giant cells without TRAP activity (TRAP-staining, 400x magnification; scale bar = 100  $\mu$ m);
- e) inner region of the implantation bed. (arrows: mononuclear cells; asterisks: ) aqueous polymer solution (Movat's pentachrome staining, 200x magnification; scale bar = 100  $\mu$ m).

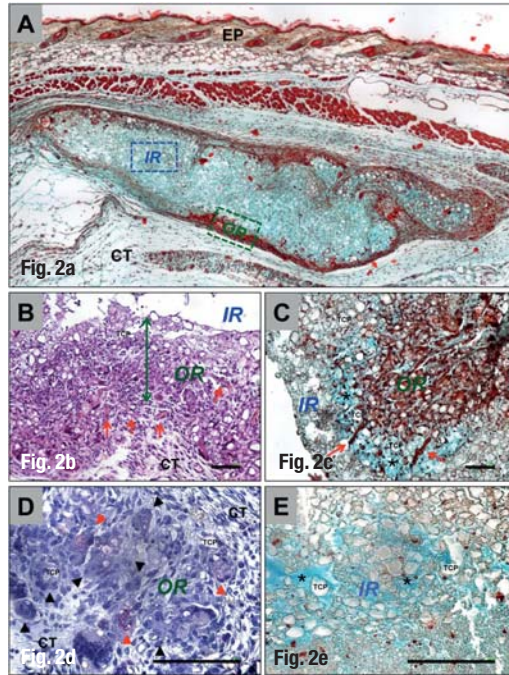

our and the vascularisation of a new paste-like bone-substitute material composed of  $\beta$ -TCP, methylcellulose (MC) and hyaluronic acid (HY) by means of histological and histomorphometrical analysis. Therefore, the cellular tissue reaction to this new bone substitute material was investigated in the subcutaneous implantation model in Wistar rats during an observation period of 60 days. Three groups with (a) subcutaneous implantation of pure, solid  $\beta$ -TCP, (b) subcutaneous injection of sodium chloride, and (c) a sham operated animals served as controls.

## Material and methods

### Bone substitute material

In the present study an injectable bone substitute paste made from crushed pure-phase  $\beta$ -TCP, methylcellulose and hyaluronic acid was investigated. The manufacturing process of sintering and crushing results in ceramic particles with a size of  $<63 \mu$ m, which were mixed with an aqueous polymer solution in a ratio of 70 wt% ceramics and 30 wt% polymer solution.

### Study design

With approval from the Committee on the Use of Live Animals in Teaching and Research of the State of Rhineland-Palatinate, Germany, 90 female, 5-week-old Wistar rats were divided in three groups and received implantation of the above mentioned injectable  $\beta$ -tricalcium phosphate bone substitute material (group 1) and pure, solid  $\beta$ -TCP granules (group 2). For control, ten animals underwent an operation with an injection of sodium chloride (group 3) and another 20 animals (group 4) underwent preparation of subcutaneous pockets without biomaterial implantation. At 3, 10, 15, 30 and 60 days, the animals were sac-

rificed by an overdose of ketamine and xylazine and according to a previously described method<sup>9, 36-39</sup> the bone substitute material was explanted and processed for histological and histomorphometrical analysis.

### Tissue preparation

The extracted samples were fixed in 4% formalin, cut into segments of 4 mm thickness, decalcified, dehydrated in alcohol and embedded in paraffin. Afterwards the samples were cut with a microtome in sections of a thickness of 4  $\mu$ m and stained as follows: the first section was stained with haematoxylin and eosin (H&E), the second section with tartrate-resistant acid phosphatase (TRAP) to identify osteoclast-like cells, while the third and fourth section were used for immunochemical staining with ED-1 antibody (for cells of the monocyte-macrophage lineage). A fifth slide was stained with Movat's pentachrome to visualise connective tissue ingrowth within the implantation bed and a seventh slide was stained by von Kossa/Safranin-O staining for identification of calcium and calcium phosphates.<sup>9, 36-41</sup>

### Histological and histomorphometrical investigation

After staining, the sections were investigated by independent investigators with a diagnostic microscope (Nikon, Tokyo, Japan) and the tissue-biomaterial interaction within the implantation bed and the peri-implant tissue was examined histomorphometrically using the NIS-Elements software (Nikon, Tokyo, Japan). The total number of vessels and their area on each slide were determined and related to the total implantation area. Thereby, for each time point, a mean number of vessels per square millimetre and a mean total vessel area could be determined. The results of the quantitative analysis were presented as mean  $\pm$  standard deviation with differences considered significant if p-values were  $<0.05$  (\* $p < 0.05$ ) and highly significant if p-values were  $<0.01$  (\*\* $p < 0.01$ ).

## Results

All the animals in each group survived the surgical procedures and the postoperative observation period without complications. No signs for severe inflammatory response were observed.

### Tissue reaction to $\beta$ -TCP granules

Beginning on day 3, the  $\beta$ -TCP granule group material induced penetration of phagocytes, macrophages and connective tissue fibres, resulting in a poorly vascularised fiber and fibroblast rich granulation tissue, which had completely penetrated the implantation bed at day 15. At day 30 and 60 only few remnants of the bone substitute granules were obvious. The vascularisation of the implantation bed remained low, presenting no significant differences in



the aforementioned vascularisation parameters to the results of the two control groups (Figs. 7a-d, 8a & b):

*Tissue reaction to paste-like  $\beta$ -TCP solution*

Within the implantation bed of the triphasic paste-like  $\beta$ -TCP at day 3, the bone-substitute material appeared as a compact structure. The implanted material could be divided in compact outer surface and an inner core. A large number of phagocytes, lymphocytes, a few plasma cells and eosinophils and connective tissue fibres started to penetrate the outer surface without reaching the inner core. Therefore neither vessels nor connective tissue or organic structures were found in the central parts of the implantation bed (Figs. 1a-c).

At day 10 the separation within the biomaterial was still present. The outer structure contained an active granulation tissue, with an increased vascularisation by newly formed vessels, while the inner core, comparable to day 3, was still populated by very few mononuclear cells (Figs. 2a-e).


At day 15, the degradation of the outer structure proceeded. The granulation tissue formed around the biomaterial was rich in vessels and contained more multinucleated giant cells than at day 10. In the inner core still less connective tissue fibres and mononuclear and especially multinuclear cells were detectable compared to the outer regions (Figs. 3a-d).

The implantation bed showed total integration of the inner and outer part of the implanted biomaterial at day 30. TRAP positive multinucleated giant cells dominated the fiber and vessel rich granulation tissue. The former outer region had been transformed into a connective tissue with very few phagocytes and rich in fibres, while the inner core of the implant had been transformed into a richly vascularized granulation tissue (Figs. 4a & c).


To the end of the observation at day 60 the degradation of the biomaterial, mainly by multinucleated giant cells continued. In areas, where biomaterial remnants were still present, granulation tissue was still present, while in parts where the biomaterial was already completely degraded, it was replaced by adipose and connective tissue. Remaining granules were surrounded by phagocytes, i.e. macrophages and multinucleated giant cells (Figs. 5a & c, 6a-d).

*Histomorphometric results*

Histomorphometric investigation of the explanted biomaterials was performed to determine the vascularisation within the implantation bed at different time points of biomaterial integration. At day 3 a mild vascularisation within the three phasic injectable

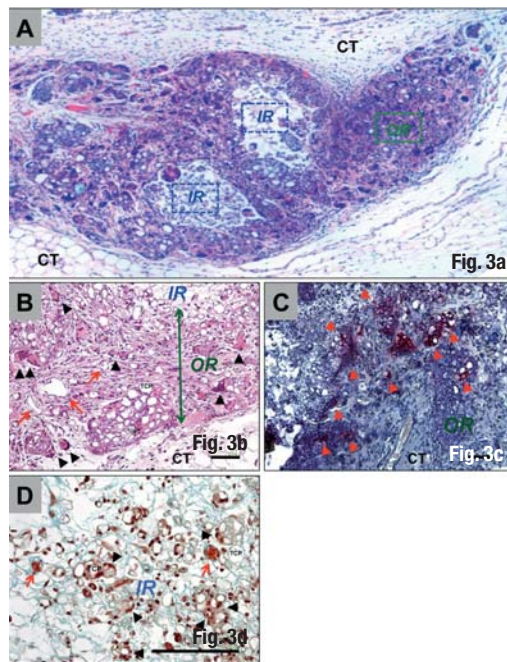

**Fig. 3** The tissue reaction to the triphasic bone-substitute material at day 15 after implantation; a) overview of the implanted material within the subcutaneous connective tissue (CT). (H&E-staining, total scan, 100x magnification); b) outer region (OR, double head arrow), with a unique granulation tissue (red arrows: vessels; arrow heads: multinucleated giant cells; (H&E-staining, 200x magnification; scale bar = 100  $\mu$ m); c) TRAP activity in multinucleated giant cells (red arrow heads; TRAP staining, 200x magnification; scale bar = 100  $\mu$ m); d) the composition of the inner region (IR) of the implanted material. (arrow heads: multinucleated giant cells; red arrows: vessels; black arrows: mononuclear cells (Movat's pentachrome staining, 400x magnification; scale bar = 100  $\mu$ m).

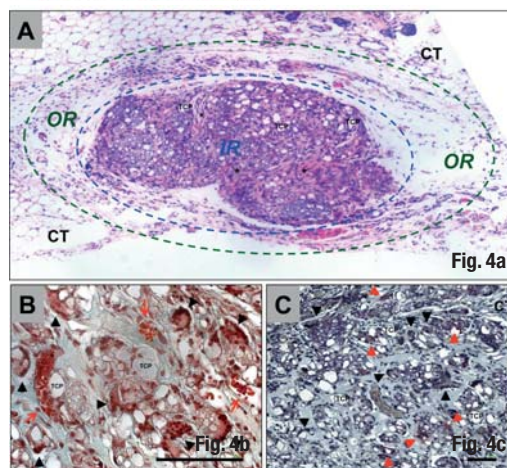

**Fig. 4** The tissue reaction to the triphasic bone-substitute material at day 30 after implantation; a) total scan of the implant region. Inner circle with few bone substitute remnants (asterisks: granulation tissue; H&E staining, total scan, 100x magnification); b) the former inner region transformed into a granulation tissue. (red arrows: vessels; arrow heads: multinucleated giant cells; Movat's pentachrome staining, 400x magnification; scale bar = 100  $\mu$ m); c) differential TRAP expression at this time point shown by TRAP-negative and TRAP-positive multinucleated giant cells (black arrow heads: TRAP- negative multinucleated giant cells; red arrow heads: TRAP- positive multinucleated giant cells; TRAP-staining, 200x magnification; scale bar = 100  $\mu$ m).

$\beta$ -TCP biomaterial, which was significantly higher than in the  $\beta$ -TCP granule group, was observed (\*\* $p < 0.01$ , Figs. 8a & b). At days 10, 15, 30 and 60 significantly higher values for percent vascularisation and vessel density in the  $\beta$ -TCP paste were observed compared to the solid  $\beta$ -TCP and the two control groups (sham operation and sodium chloride). These data indicated a maturing of the vessels within the implant. A detailed overview of the significance levels between the different groups at each time point is given in figure 8a & b.

**\_Discussion**

In the present study the tissue reactions to a paste-like bone substitute material composed of  $\beta$ -TCP, methylcellulose and hyaluronic acid was investigated in the subcutaneous implantation model in Wistar rats over 60 days. Implantation of pure solid  $\beta$ -TCP, injection of sodium chloride and sham operation served as controls. The primary focus of histological and his-